

Application of the kinetic and isotherm models for better understanding of the behaviors of silver nanoparticles adsorption onto different adsorbents

by Achmad Syafiuddin

Submission date: 07-Sep-2018 08:55AM (UTC+0700)

Submission ID: 998020448

File name: Journal_Internasional_bereputasi_2018_Q1_JB.pdf (562.19K)

Word count: 10557

Character count: 57292



Contents lists available at ScienceDirect

Journal of Environmental Management

journal homepage: www.elsevier.com/locate/jenvman

Review

Application of the kinetic and isotherm models for better understanding of the behaviors of silver nanoparticles adsorption onto different adsorbents



164 Achmad Syafiuddin^a, Salmiati Salmiati^{a, b}, Jonbi Jonbi^c, Mohamad Ali Fulazzaky^{c, d, e, *}

^a Department of Environmental Engineering, Faculty of Civil Engineering, Universiti Teknologi Malaysia, 81310 UTM Skudai, Johor Bahru, Malaysia

^b Centre for Environmental Sustainability and Water Security, Research Institute for Sustainable Environment, Universiti Teknologi Malaysia, 81310 UTM Skudai, Johor Bahru, Malaysia

^c Faculty of Civil Engineering, Pancasila University, Jalan Kenseng Sawah, Jakarta 12640, Indonesia

^d Islamic Science Research Network, University of Muhammadiyah Prof Dr Hamka, Jalan Limau No. 2, Jakarta, 12130, Indonesia

^e Directorate General of Water Resources, Ministry of Public Works and Housing, Jalan Pattimura No. 20, Jakarta, 12110, Indonesia

88

ARTICLE INFO

Article history:

Received 20 November 2017

Received in revised form

12 March 2018

Accepted 14 March 2018

Keywords:

Adsorption isotherm model

Adsorption kinetic model

Arithmetic mean

Natural adsorbent

Silver nanoparticles

Synthetic adsorbent

A B S T R A C T

150 It is the first time to do investigation the reliability and validity of thirty kinetic and isotherm model¹⁰⁵ describing the behaviors of adsorption of silver nanoparticles (AgNPs) onto different adsorbents. The purpose of this study is therefore to assess the most reliable models for the¹³¹ adsorption of AgNPs onto feasibility of an adsorbent. The fifteen kinetic models and fifteen isotherm models were used to test secondary data of AgNPs adsorption collected from the various data sources. The rankings of arithmetic mean were estimated based on the six statistical analysis methods of using a dedic⁷² software of the MATLAB Optimization Toolbox with a least square curve fitting function. The use of fractal-like mixed 1, 2-order model for describing the adsorption kinetics and that of Fritz-Schlunder and Baudu models for describing the adsorption isotherms can be recommended as the most reliable models for AgNPs adsorption onto the natural and synthetic adsorbent materials. The application of thirty models have been identified for the adsorption of AgNPs to clarify the usefulness of both groups of the kinetic and isotherm equations in the rank order of the levels of accuracy, and this significantly contributes to understandability and usability of the proper models and makes to knowledge beyond the existing literatures.

© 2018 Elsevier Ltd. All rights reserved.

Contents

95	1. Introduction	60
	2. Materials and methods	61
	2.1. Data collection	61
	2.2. Numerical simulation	61
	2.2.1. Adsorption kinetic models	61
	2.2.2. Adsorption isotherm models	62
	2.3. Error analysis for application of the kinetic and isotherm models	63
	3. Results and discussion	64
	3.1. Results	64
	3.1.1. Adsorption of AgNPs on glass beads	64
	3.1.2. Adsorption of AgNPs on aged iron oxide magnetic particles	64
	3.1.3. Adsorption of AgNPs on Fe ₃ O ₄ @ polydopamine core-shell microspheres	65

53

* Corresponding author. Directorate General of Water Resources, Ministry of Public Works and Housing, Jalan Pattimura, 52, Jakarta, 12110, Indonesia.
E-mail address: fulazzaky@gmail.com (M.A. Fulazzaky).

<https://doi.org/10.1016/j.jenvman.2018.03.066>

0301-4797/© 2018 Elsevier Ltd. All rights reserved.

3.1.4.	Adsorption of AgNPs on Poly(ethylenimine) functionalized core-shell magnetic	65
3.1.5.	Adsorption of AgNPs on <i>Aeromonas punctata</i>	65
3.2.	Discussion	66
3.2.1.	Application of the adsorption kinetic models	66
3.2.2.	Application of the adsorption isotherm models	66
4.	Conclusions	68
	Conflict of interest	69
	Acknowledgements	69
	Supplementary data	69
	References	69

122

1. Introduction

Silver nanoparticles (AgNPs) have been widely used in many industrial applications due to they have many advantageous properties of such as antibacterial, antifungal, antiviral, anti-inflammatory, anti-angiogenic and anticancer agents, as well as high electrical conductivity and high sensitivity (Desireddy et al., 2013; Kumar et al., 2008; Le Ouay and Stellacci, 2015; Naik et al., 2002; Park et al., 2012; Zhang et al., 2016). However, the excessive amount of AgNPs released from industrial products of such as detergents, textiles, toys, cosmetics and medical devices can have the potential to cause the risks to human health and the environment because of its antimicrobial effects and subsequent practical applications, and the presence of AgNPs in the environment poses undesirable effects on plants of being inhibited seed germination and growth and has substantial adverse to microbial communities in engineered or natural ecosystems (Chen et al., 2017; Quadros and Marr, 2010; Tripathi et al., 2017). The content of AgNPs released from industrial products becomes more important and concerned in many countries because it can cause toxicity to aquatic biota near sources such as sewage discharges.

Adsorption found to be effective and cheap method among the available heavy metals removal methods and has been widely used to remove AgNPs from water. The use of nitrogen rich core-shell magnetic mesoporous silica as adsorbent has been proven to be effective for the removal of AgNPs from water with an adsorption capacity of 909.1 mg g⁻¹ (Zhang et al., 2017). The use of glass beads as adsorbent can remove up to 75% of AgNPs (Polowczyk et al., 2015). The use of aged iron oxide magnetic particles synthesized by a simple solvothermal method can remove up to 90% of AgNPs for a contact time of 90 min (Zhou et al., 2017). The elimination of AgNPs from synthetic wastewater by electrocoagulation has been proven to be effective by using four different routes (Matias et al., 2015).

Many theoretical and empirical models have been proposed for describing mechanisms of AgNPs adsorption from aqueous solution. However, the report provides practical guidance for choosing an appropriate method by comparing two, three or four models only. Four kinetic models of Lagergren pseudo-first-order, pseudo-second-order, Elovich and intraparticle diffusion have been tested for modeling the adsorption kinetics of AgNPs from aqueous solution to justify that two-parameter equations of pseudo-second-order showed more applicability than six-parameter equations of pseudo-first-order, Elovich and intraparticle diffusion (Ruiz-Baltazar et al., 2015). Application of four kinetics models and three isotherm models has been proposed for simulating the experimental data of AgNPs adsorption onto different adsorbents to show that all the data can have a better fit for both the kinetic model of pseudo-second-order and the isotherm model of Langmuir (Zhou et al., 2017). Two kinetic models (i.e., pseudo-first-order and pseudo-second-order) and three isotherm models (i.e.,

Dubinin-Radushkevich, Freundlich and Langmuir) have been proposed to test the experimental data of AgNPs adsorption and confirmed that using the pseudo-second-order and Langmuir model can get more accurate estimates of the parameter equations (Wu et al., 2017). The use of two kinetic models (i.e., pseudo-first-order and pseudo-second-order) and two isotherm models (i.e., Freundlich and Langmuir) has been used to simulate the experimental data of AgNPs adsorption to show that most reliable estimates of the parameter equations were found with the pseudo-second-order and Langmuir models (Zhang et al., 2017). The use of Langmuir model has been proven to be better than that of Freundlich model for describing the adsorption of AgNPs on the surface of sodium montmorillonite nanoclays (Zarei and Barghak, 2015). Three models of pseudo-first-order, pseudo-second-order and Langmuir have been used to explain many observations in adsorption of AgNPs on the surface of a natural material of added *Aeromonas punctata* strain to show that the experimental data were fit well with Langmuir and pseudo-second-order models (Khan et al., 2012). Modeling of experimental data for the adsorption of AgNPs from aqueous solution using the copper-based metal organic framework nanoparticles would fit well with the pseudo-second-order and Langmuir models, and the Langmuir isotherm does describe equilibrium behavior better than the Freundlich isotherm due to the adsorption does not continue beyond a monolayer (Conde-González et al., 2016). However, the experimental data for the adsorption of AgNPs on commercial activated carbon showed that the Freundlich isotherm can describe equilibrium behavior better than the Langmuir isotherm because of the adsorption continues beyond a monolayer (Gicheva and Yordanov, 2013). The conclusions obtained from different studies did show that the usefulness of statistical tests in model validation for the adsorption of AgNPs on the surface of a material is very limited.

The interpretation of adsorption isotherms has been reviewed for the applications of one one-parameter isotherm of Henry's model, thirteen two-parameter isotherms of Hill-Deboer, Fowler-Guggenheim, Langmuir, Freundlich, Dubinin-Radushkevich, Temkin, Flory-Huggins, Hill, Sips, Harkin-Jura, Jovanovic, Elovich and Kiselev models, eight three-parameter isotherms of Redlich-Peterson, Sips, Toth, Koble-Carrigan, Kahn, Radke-Prausnits, Langmuir-Freundlich and Jossens models, four four-parameter isotherms of Fritz-Schlunder, Baudu, Weber-Van Vliet and Marczewski-Jaroniec models, and one five-parameter isotherm model developed by Fritz and Schlunder whereas the error analysis was performed using the nine methods of Sum of Square of Errors (ERRSQ), Hybrid Fractional Error Function (HYBRID), Average Relative Error (ARE), Marquardt's Percent Standard Deviation (MPSD), Sum of Absolute Errors (EABS), Sum of Normalized Errors (SNE), Coefficient of Determination (R^2), Nonlinear Chi-Square Test (X^2), Coefficient of Nondetermination ($1.00 - R^2$). This review concludes that the level of accuracy would be dependent on the successful modeling and interpretation of adsorption isotherms

(Ayawei et al., 2017). Even if the mass transfer factor (MTF) models to describe the adsorption kinetics of AgNPs solely in water (Fulazzaky, 2011, 2012) and the modified MTF models to describe the adsorption kinetics of AgNPs accompanied with multifarious solute in water (Fulazzaky et al., 2011, 2014; 2017) have not been used to possibly distinguish between the film mass transfer and the porous diffusion and to determine the resistance of mass transfer, it could be a challenge of verifying the possibility of using many other mathematical models to understand the behaviors of AgNPs adsorption. The aim of this study was to evaluate the use of fifteen kinetic models and that of fifteen isotherm models for describing the behaviors of AgNPs adsorption onto different adsorbents from aqueous solution. In the present work, the use of dedicated software program of the MATLAB Optimization Toolbox with a least square curve fitting (lsqcurvefit) function can be used as a framework to systematically manipulate and compare the application of six statistical methods of analysis toward a better understanding of the adsorption behaviors of AgNPs.

2. Materials and methods

2.1. Data collection

The data of AgNPs adsorption provided by secondary data sources were used as input to a numerical simulation process. The biological and non-biological adsorbent materials were all considered being testable in this study. The experimental data of AgNPs adsorption onto the synthetic materials of glass beads (GB) collected by Polowczyk et al. (2015), aged iron oxide magnetic particles (AIOMP) collected by Zhou et al. (2017), Fe₃O₄@ polydopamine core-shell microspheres (FPC) collected by Wu et al. (2017) and poly(ethyleneimine) functionalized core-shell magnetic mesoporous silica composites (PFC) collected by Zhang et al. (2017) as well as those onto the natural (biological) material of using the strains of *Aeromonas punctata* (AP) collected by Khan et al. (2012) were reviewed to assess the reliability of a model and to compare different models.

2.2. Numerical simulation

2.2.1. Adsorption kinetic models

This study used the fifteen kinetic models to assess the behaviors of AgNPs adsorption onto different materials. To date, some of these models have been used as systemic approaches to simulate the secondary data (Khan et al., 2012; Polowczyk et al., 2015; Wu et al., 2017; Zhang et al., 2017; Zhou et al., 2017) in spite of many other models such as the MTF and modified MTF models (Fulazzaky, 2011, 2012; Fulazzaky et al., 2013, 2014; 2017) are still not considered for the analysis of the data.

In this work, the first-order model as proposed by Gupta et al. (2001) for dynamic modeling of lead and chromium removal from aqueous solution on red mud was used to assess the reasonableness of accounting its two-parameter equations and this can be mathematically written as follows:

$$q_t = q_e - \exp(-k_1 t) \quad (1)$$

where q_t is the adsorption capacity (mg g^{-1}) at time t (min), q_e is the adsorption capacity at equilibrium (mg g^{-1}), and k_1 is the first-order rate constant (min^{-1}).

The Ritchie second-order model has been used to describe the adsorption of cadmium ions from effluents using bone char (Cheung et al., 2001; Khambhaty et al., 2009) as:

$$q_t = \frac{q_e}{1 + q_e k_2 t} \quad (2)$$

where k_2 is the second-order rate constant (min^{-1}).

The pseudo-first-order model, firstly proposed by Lagergren (1898) to describe the kinetic process of liquid-solid phase adsorption of oxalic acid and malonic acid onto charcoal and used by Ho and McKay (1998a) to describe the pseudo-first order sorption kinetics of phosphate onto tamarind nut shell activated carbon, can be mathematically written as the following formula:

$$q_t = q_e [1 - \exp(-k_{p1} t)] \quad (3)$$

where q_e is the adsorption capacity at equilibrium (mg g^{-1}), and k_{p1} is the pseudo-first-order rate constant (min^{-1}).

A kinetic model pseudo-second-order as proposed by Ho and McKay (1998b) to describe the chemisorption of divalent metal ions onto peat may be used to compare protocols and tests and this can be expressed as follows:

$$q_t = \frac{k_{p2} q_e^2 t}{1 + k_{p2} q_e t} \quad (4)$$

where k_{p2} is the pseudo-second-order rate constant (min^{-1}).

The intraparticle diffusion model (Plazinski and Rudzinski, 2009) to describe the transportation of species from the bulk to solid phase of porous material in solution may take the following form:

$$q_t = k_{ip} \sqrt{t} + c_{ip} \quad (5)$$

where k_{ip} is the measure of diffusion coefficient ($\text{mg g}^{-1} \text{min}^{-1/2}$) and c_{ip} is the intraparticle diffusion constant (mg g^{-1}).

A power model of describing the adsorption behaviors as proposed by Khambhaty et al. (2009) can be mathematically written as follows:

$$q_t = k_p t^{v_p} \quad (6)$$

where k_p and v_p are the power constants of the model.

The Avrami's model to describe the kinetics of phase transformation under the assumption of spatially random nucleation has been used for assessing the adsorption of either methylene blue or Hg(II) from aqueous solution (Lopes et al., 2003; Royer et al., 2009) and can be expressed by the following equation:

$$q_t = q_e [1 - \exp(-k_{av} t)^{n_{av}}] \quad (7)$$

where k_{av} the Avrami rate constant (min^{-1}) and n_{av} is the Avrami component (dimensionless).

The Bangham model has been used to describe the adsorption of anionic and cationic dyes on activated carbon from aqueous solution (Rodríguez et al., 2009) and can be written in the form of:

$$q_t = k_b t^{1/m} \quad (8)$$

where k_b is the adsorption rate constant ($\text{mg g}^{-1} \text{min}^{-1}$) and m is the indicator of adsorption intensity (dimensionless).

A kinetic model derived from the pseudo-first-order and pseudo-second-order called the mixed 1, 2-order model as proposed by Marczewski (2010) to assess the kinetics of dye adsorption onto mesoporous carbons from aqueous solution can be proposed in this work to assess the behaviors of AgNPs adsorption. The formula of the mixed 1, 2-order model can be written as follows:

$$q_t = q_e \frac{1 - \exp(-kt)}{1 - f_2 \exp(-kt)} \quad (9)$$

where f_2 is the mixed 1,2-order coefficient (dimensionless) and k is the adsorption rate constant ($\text{mg g}^{-1} \text{min}^{-1}$).

An exponential form of the kinetic equation (Haerifar and Azizian, 2013) can be used to describe the pattern of adsorption rate with time where its mathematical equation can be written in the following form:

$$q_t = q_e \ln[2.72 - 1.72 \exp(-k_e t)] \quad (10)$$

where k_e is the constant of the exponential model ($\text{mg g}^{-1} \text{min}^{-1}$).

A modified exponential model called as the fractal-like exponential model has been proposed by Haerifar and Azizian (2013) for the adsorption on heterogeneous solid surface and can be written in the form of:

$$q_t = q_e \ln[2.72 - 1.72 \exp(-k_{\text{fle}} t^\alpha)] \quad (11)$$

where k_{fle} is the fractal-like exponential rate coefficient ($\text{mg g}^{-1} \text{min}^{-1}$) and α is the constant of the model (dimensionless).

The Boyd's model as proposed by Kumar et al. (2014) to predict the actual slowest step in the adsorption process and by Viegas et al. (2014) for estimating intraparticle diffusion coefficients in adsorption processes can be used to assess the behaviors of AgNPs adsorption and this can be expressed as:

$$q_t = q_e \left[1 - \frac{6}{\pi^2} \exp(-Bt) \right] \quad (12)$$

where B is the coefficient that covers the effective diffusion process and radius of the particles (min^{-1}).

A modification of the pseudo-first-order model called as the Fractal-like pseudo-first-order model has been proposed by Haerifar and Azizian (2014) to introduce the fractal concept and can be written as:

$$q_t = q_e \left[1 - \exp(-k_{\text{ffo}} t^\alpha) \right] \quad (13)$$

where k_{ffo} is the fractal-like pseudo-first-order coefficient ($\text{mg g}^{-1} \text{min}^{-1}$) and α is the fractal-like pseudo-first-order model constant.

A modification of the pseudo-second-order model called as the fractal-like pseudo-second-order model proposed by Haerifar and Azizian (2014) to introduce the fractal concept can be mathematically written as:

$$q_t = \frac{k_{\text{fso}} q_e^2 t^\alpha}{1 + k_{\text{fso}} q_e t^\alpha} \quad (14)$$

where k_{fso} is the fractal-like pseudo-second-order coefficient ($\text{mg g}^{-1} \text{min}^{-1}$) and α is the fractal-like pseudo-second-order model constant.

A modification of the mixed 1, 2-order model called as the fractal-like mixed 1, 2-order model proposed by Haerifar and Azizian (2014) to introduce the fractal concept can be written in the mathematical expression of:

$$q_t = q_e \frac{1 - \exp(-k_{\text{ffs}} t^\alpha)}{1 - f_2 \exp(-k_{\text{ffs}} t^\alpha)} \quad (15)$$

where k_{ffs} is the fractal-like mixed 1, 2-order coefficient ($\text{mg g}^{-1} \text{min}^{-1}$) and α and f_2 are the fractal-like mixed 1, 2-order model

constants.

2.2.2. Adsorption isotherm models

To do a computation of performance in adsorption system for selecting the most appropriate model, this study used the fifteen isotherm models to assess the behaviors of AgNPs adsorption onto different materials.

The Langmuir model proposed by Langmuir (1918) has been widely used to describe the adsorption occurred on homogenous surface by monolayer sorption with a finite number of identical sites such as for the adsorption of 2,4,6-trichlorophenol on coconut husk-based activated carbon (Hameed et al., 2008) and this can be mathematically expressed as:

$$q_e = \frac{K_L q_m C_e}{1 + K_L C_e} \quad (16)$$

where q_e is the adsorption capacity at equilibrium (mg g^{-1}), q_m is the maximum adsorption capacity per unit weight of the adsorbent (mg g^{-1}), C_e is the concentration of adsorbate at equilibrium (mg L^{-1}) and K_L is the Langmuir constant relating the affinity of the binding sites (L mg^{-1}).

The Freundlich model empirically developed by Freundlich (1906) could be suitable to describe sorption of several compounds to heterogeneous surfaces or surfaces supporting sites of varied affinities, assuming that stronger binding sites are occupied first and then binding strength decreases with increasing degree of site occupation (Silva et al., 2013), and can be expressed in the form of:

$$q_e = K_f C_e^{1/n} \quad (17)$$

where K_f is the Freundlich constant relating the sorption capacity (L g^{-1}) and n is the sorption intensity of adsorbent (dimensionless).

The Langmuir-Freundlich models would be suitable for describing both types of Langmuir and Freundlich adsorption isotherm (Jeppu and Clement, 2012) and can be written as:

$$q_e = \frac{q_m (K_a C_e)^n}{1 + (K_a C_e)^n} \quad (18)$$

where K_a is the affinity constant representing the degree of adsorption (L mg^{-1}) and n is the heterogeneity index.

The Redlich-Petersen model offers a compromise between two isotherm models of Langmuir and Freundlich by assuming the mechanism of adsorption is a hybrid and does not follow ideal monolayer adsorption (Wang et al., 2005) and can be formulated as follows:

$$q_e = \frac{K_{\text{RP}} C_e}{1 + a_{\text{RP}} C_e^b} \quad (19)$$

where K_{RP} and a_{RP} are the Redlich-Peterson isotherm constants (L g^{-1}) and b is the exponent that lies between 0 and 1.

The Toth model as empirical modification of the Langmuir model aims of reducing the error between experimental data and predicted values of equilibrium data (Ayawei et al., 2017; Sivarajasekar and Baskar, 2014) and can be written as:

$$q_e = \frac{q_m C_e}{(K_T + C_e^{n_T})^{1/n_T}} \quad (20)$$

where K_T is the Toth isotherm constant (mg g^{-1}) and n_T is the Toth model exponent (mg g^{-1}).

The Khan isotherm model has been used to describe the

experimental data with the minimum average percentage error for the adsorption of some pollutants from aqueous solutions by comparing several multicomponent adsorption isotherms (Ayawei et al., 2017; Khan et al., 1997) and can be expressed in the generalized mathematical expression of:

$$q_e = \frac{q_m b_K C_e}{(1 + b_K C_e)^{a_K}} \quad (21)$$

where b_K is the Khan isotherm constant ($L\ mg^{-1}$) and a_K is the Khan isotherm model exponent.

The Jovanovic model developed based on the assumptions contained in the Langmuir model with the possibility of some mechanical contacts between the adsorbing and desorbing molecules (Ayawei et al., 2017; Shahbeig et al., 2013) and can be formulated as follows:

$$q_e = q_m [1 - \exp(-K_J C_e)] \quad (22)$$

where K_J is the Jovanovic constant ($L\ g^{-1}$).

The Koble-Corrigan model proposed by Koble and Corrigan (1952) as a three-parameter equation of isotherm model which incorporates both Langmuir and Freundlich isotherms for representing equilibrium of adsorption on heterogeneous surfaces (Ayawei et al., 2017; Shahbeig et al., 2013) and can be represented by the following formula:

$$q_e = \frac{q_m a C_e^d}{1 + b C_e^d} \quad (23)$$

where a , b , and d are the Koble-Corrigan isotherm constants.

The Rake-Prausnitz model developed based on the concept of thermodynamic ideal solution by Radke and Prausnitz (1972) has several important properties which makes it more preferred in most adsorption systems to low adsorbate concentration (Ayawei et al., 2017; Sivarajasekar and Baskar, 2014) and can be expressed as:

$$q_e = \frac{q_m a_{RP} C_e}{[1 + a_{RP} C_e]^{n_{RP}}} \quad (24)$$

where a_{RP} is the Radke-Prausnitz equilibrium constant ($L\ mg^{-1}$) and n_{RP} is the Radke-Prausnitz model exponent.

The Fritz-Schlunder model proposed by Fritz and Schlunder (1974) as an empirical equation can fit a wide range of experimental data (Ayawei et al., 2017) and can be expressed as follows:

$$q_e = \frac{a_{FS} C_e^{c_{FS}}}{1 + b_{FS} C_e^{d_{FS}}} \quad (25)$$

where a_{FS} and b_{FS} are the Fritz-Schlunder equilibrium constants ($L\ g^{-1}$) and c_{FS} and d_{FS} are the Fritz-Schlunder model exponents.

The Baudu model developed from the estimation of the Langmuir coefficients model by the measurements of tangents at different equilibrium concentrations (Ayawei et al., 2017; McKay et al., 2014; Sivarajasekar and Baskar, 2014) can be expressed as follows:

$$q_e = \frac{q_m b_B C_e^{1+x+y}}{1 + b_B C_e^{1+x}} \quad (26)$$

where b_B is the Baudu equilibrium constant ($L\ mg^{-1}$), x and y are the Baudu model parameters.

The Marczewski-Jaroniec model known as the four-parameter general Langmuir equation has been developed on basis the

distribution of the supposition of local Langmuir isotherm and adsorption energies distribution in the active sites on adsorbent (Chen, 2003; Sivarajasekar and Baskar, 2014) and can be expressed by the following formula:

$$q_e = \left[\frac{q_m a_{MJ} C_e^{b_{MJ}}}{1 + a_{MJ} C_e^{b_{MJ}}} \right]^{m_{MJ}/b_{MJ}} \quad (27)$$

where a_{MJ} is the Marczewski-Jaroniec equilibrium constant ($L\ mg^{-1}$) and b_{MJ} and m_{MJ} are the Marczewski-Jaroniec model exponents.

The Hill model developed by Hill (1910) based on the assumption that adsorption is a cooperative phenomenon with adsorbates at one site of the adsorbent influencing different binding sites on the same adsorbent (Rania and Yousef, 2015) can describe the binding of different solutes onto homogeneous adsorbent and can be written as:

$$q_e = \frac{q_m C_e^{n_H}}{K_H + C_e^{n_H}} \quad (28)$$

where K_H is the Hill isotherm constant and n_H is the Hill coefficient. Notes that the values of $n_H > 1$, $n_H = 1$ and $n_H < 1$ indicate positive cooperativity, non-cooperative or hyperbolic binding and negative cooperativity in binding, respectively.

The Brouers-Sotolongo model is an adsorption isotherm model given by a deformed exponential function of Weibull distribution (Podder and Majumder, 2016) and this can be written by the following formula:

$$q_e = q_m [1 - \exp(-K_{BS} C_e^{n_{BS}})] \quad (29)$$

where K_{BS} is the Brouers-Sotolongo equilibrium constant ($L\ mg^{-1}$) and n_{BS} is the Brouers-Sotolongo model exponent.

The Unilin model is one of the empirical correlations to express experimental data for representing the adsorption (Valenzuela and Myers, 1989) and can be mathematically formulated as follows:

$$q_e = \frac{q_m}{2b_U} \ln \left(\frac{a_U + C_e \exp(b_U)}{a_U + C_e \exp(-b_U)} \right) \quad (30)$$

where a_U is the Unilin equilibrium constant and b_U is the Unilin model exponent.

2.3. Error analysis for application of the kinetic and isotherm models

This study used the dedicated software of the MATLAB Optimization Toolbox with its lsqcurvefit function to simulate and analyze the experimental data of AgNPs adsorption on the natural and synthetic adsorbent materials. The algorithms can perform calculation, data processing and automated reasoning tasks based on the nonlinear lsqcurvefit function found in the MATLAB to find the coefficient of determination (R^2), root mean squared error (RMSE), percentage of error in maximum estimated value (E_{max}), percentage of error in minimum estimated value (E_{min}), mean absolute percent error (MAPE) and mean absolute deviation (MAD) for statistical analysis significance tests for all the kinetic and isotherm models. The first condition induces a ranking of the arithmetic mean for every model in terms of accuracy. Because of the arithmetic mean is the most commonly used and readily understood measure of central tendency, the selection of a potential model with comparison of the other models as a function of the number of terms in each model is based on the arithmetic mean

information criteria. Finally, the best model order can be determined using the minimum value of average ranking (AR). The mathematical equation of the statistical analysis methods can be described as follows:

(1) For the coefficient of determination,

$$R^2 = 1 - \frac{\sum (x_{obs,i} - x_{model,i})^2}{\sum (x_{obs,i} - \bar{x}_{obs})^2} \quad (31)$$

(2) For the root mean squared error,

$$RMSE = \sqrt{\frac{\sum_{i=1}^n (x_{obs,i} - x_{model,i})^2}{n}} \quad (32)$$

(3) For the percentage of error in maximum estimated value,

$$E_{max} = \left| \frac{x_{model,max} - x_{obs,max}}{x_{obs,max}} \right| \times 100\% \quad (33)$$

(4) For the percentage of error in minimum estimated value,

$$E_{min} = \left| \frac{x_{model,min} - x_{obs,min}}{x_{obs,min}} \right| \times 100\% \quad (34)$$

(5) For the mean absolute percent error,

$$MAPE = \left(\frac{1}{n} \sum \frac{|x_{obs,i} - x_{model,i}|}{|x_{obs,i}|} \right) \times 100\% \quad (35)$$

(6) For the mean absolute deviation,

$$MAD = \frac{1}{n} \sum |x_{obs,i} - x_{model,i}| \quad (36)$$

where $x_{obs,i}$ is the data obtained from observation at time i , $x_{model,i}$ is the data modeled for observation at time i , n is the number of data, $x_{obs,max}$ is the maximum value of the modeled data, $x_{obs,max}$ is the maximum value of the observed data, $x_{model,min}$ is the minimum value of the modeled data, and $x_{obs,min}$ is the minimum value of the observed data.

3. Results and discussion

3.1. Results

The requirement to define a proper model for the adsorption of AgNPs onto different adsorbents has been becoming a concern in terms of AgNPs removal (Sheng and Liu 97 17). In this work, the following criteria were used to rank the goodness-of-fit testing of the kinetic and isotherm models to experimental data that the value of $AR < 3.75$, that of $3.75 \leq AR \leq 7.50$, that of $7.50 < AR \leq 11.25$ and that of $11.25 < AR \leq 15$ represent the very good, good, satisfactory and poor adsorption performance, respectively. The results of ranking the values of every statistical analysis method for 44 adsorption of AgNPs onto different adsorbents were analyzed on the basis of measuring the values of the parameter equations of each model (see Tables 1 and 2 in Supplementary 141 materials) and can be then used to verify if one kinetic or isotherm model could fit the data better than others.

3.1.1. Adsorption of AgNPs on glass beads

The results (Table 3 in Supplementary materials) of ranking the values of arithmetic mean being obtained from every statistical analysis method for the kinetic models of AgNPs adsorption on GB show that the statistical analysis for the fractal-like mixed 1, 2-

order, fractal-like pseudo-first-order and fractal-like exponential models gives a very good fit to experimental data as their AR values of 1.2, 2.3 and 3.3, respectively, have been verified with a best fit being obtained for the fractal-like mixed 1, 2-order model due to its lowest AR value of 1.2. A good fit can be obtained for the fractal-like pseudo-second-order, Power, Boyd and Bangham models as their AR values of 3.8, 5.5, 5.7 and 6.2, respectively, were verified. The model-data fit can be considered satisfactory for the intraparticle diffusion, pseudo-second-order, mixed 1, 2-order and exponential models since the AR values were verified as high as 8.3, 9.3, 9.3 and 22, respectively. The statistical analysis for the pseudo-first-order, first order, Avrami and second-order models gives a poor fit to the data due to their AR values of 13.0, 13.2, 13.3 and 14.3, respectively, were verified and this reveals a very poor fit being obtained for the second-order model because of its AR value of 14.3 is higher than others.

The analysis of using the values of arithmetic mean for the isotherm models of AgNPs adsorption on GB (see Table 4 in Supplementary materials) shows that the Fritz-Schlunder and Baudu models give a very good fit to experimental data as their AR values of 1.67 and 2.67, respectively, have been verified with a best fit being obtained for the Fritz-Schlunder model verified by its lowest AR value of 1.67. A good fit can be found for the Khan, Toth and Radke-Prausnitz models as it can be verified by observation of their AR values of 3.67, 4.17 and 4.67, respectively. The verification of model-data fit carried out using the Brouers-Sotolongo, Hill, Redlich-Peterson, Jovanovic, Maczewski-Jaroniec, Koble-Corrigan and Langmuir models can be considered satisfactory since this view deals with the AR values as high as 7.67, 8.00, 8.17, 9.33, 10.00, 10.38 and 11.17, respectively. The statistical data analysis gives a poor fit for the Langmuir-Freudlich, Unilin and Freundlich models as it has been verified by the observation of the AR values as high as 12.00, 12.17 and 13.83, respectively, and this verification reveals a very poor fit for the Freundlich model due to its AR value of 13.83 is higher than others.

3.1.2. Adsorption of AgNPs on aged iron oxide magnetic particles

The results (Table 5 in Supplementary materials) of numerical simulation by the kinetic models of AgNPs adsorption on AIOMP show that the statistical analysis for the fractal-like mixed 1, 2-order, mixed 1, 2-order and fractal-like pseudo-first-order kinetic models gives a very good fit to experimental data as their AR values of 1.33, 1.83 and 2.83, respectively, have been verified with a best fit being obtained for the fractal-like mixed 1, 2-order model due to its lowest AR value of 1.33. A good fit can be obtained for the fractal-like exponential, fractal-like pseudo-second-order, pseudo-first-order and Avrami models since their AR values of 4.00, 5.00, 6.33 and 7.00, respectively, were verified. The model-data fit can be considered satisfactory for the exponential, pseudo-second order and power models because of the AR values were verified as high as 8.17, 9.17 and 10.67, respectively. The statistical analysis for the Bangham, Boyd, intraparticle diffusion, first-order and second-order models gives a poor fit to the data due to their AR values of 11.33, 11.33, 12.00, 14.33 and 14.67, respectively, were verified and this reveals a very poor fit being obtained for the second-order model because of its AR value of 14.67 is higher than others.

The analysis of using the values of arithmetic mean for the isotherm models of AgNPs adsorption on AIOMP (see Table 6 in Supplementary materials) shows that the only Brouers-Sotolongo model gives a very good fit to experimental data due to its AR value of 1.00 has been verified. A good fit can be found for the Langmuir-Freudlich, Fritz-Schlunder, Baudu, Koble-Corrigan, Hill, Maczewski-Jaroniec and Jovanovic models as it can be verified by observation of their AR values of 4.00, 4.50, 4.50, 4.67, 4.83, 5.50 and 7.00, respectively. The verification of model-data fit carried out

using the Toth, Khan and Radke-Prausnitz models can be considered satisfactory since this view deals with the AR values as high as 9.67, 9.83 and 10.50, respectively. The statistical data analysis gives a poor fit for the Langmuir, Unilin, Redlich-Peterson and Freundlich models as it has been verified by the observation of the AR values as high as 12.33, 12.67, 14.33 and 14.67, respectively, and this verification reveals a very poor fit for the Freundlich model due to its AR value of 14.67 is higher than others.

3.1.3. Adsorption of AgNPs on Fe_3O_4 @ polydopamine core-shell microspheres

The results (Table 7 in Supplementary materials) of ranking the values of arithmetic mean being obtained from every statistical analysis method for the kinetic models of AgNPs adsorption on PFC show that the statistical analysis for the fractal-like mixed 1, 2-order and pseudo-second order models gives a very good fit to experimental data because of their AR values of 1.17 and 2.83, respectively, have been verified with a best fit being obtained for the fractal-like mixed 1, 2-order model to its lowest AR value of 1.17. A good fit can be obtained for the pseudo-first-order, first order, exponential, Boyd and Avrami models since their AR values of 4.83, 5.17, 5.33, 5.33 and 5.83, respectively, were verified. The model-data fit can be considered satisfactory for the fractal-like exponential, Bangham, power, fractal-like pseudo-first-order and mixed 1, 2-order models since their AR values were verified as high as 9.33, 10.00, 11.7, 10, 50, and 11.17, respectively. The statistical analysis for the fractal-like pseudo-second order, intraparticle diffusion and second-order models gives a poor fit to the data because of their AR values of 11.50, 12.17 and 14.67, respectively, were verified and this reveals a very poor fit being obtained for the second-order model due to its AR value of 14.67 is higher than others.

The analysis of using the values of arithmetic mean for the isotherm models of AgNPs adsorption on PFC (see Table 8 in Supplementary materials) shows that the only Koble-Corrigan model give a very good fit to experimental data as its AR value of 2.17 has been verified. A good fit can be found for the Toth, Khan, Brouers-Sotolongo, Fritz-Schlunder, Baudu, Langmuir-Freudlich and Maczewski-Jaroniec models as it can be verified by observation of their AR values of 3.67, 4.00, 5.17, 6.33, 6.33, 6.67 and 7.00, respectively. The verification of model-data fit carried out using the Hill, Jovanovic and Langmuir models can be considered satisfactory since this view deals with their AR values as high as 9.33, 9.50 and 9.83, respectively. The statistical data analysis gives a poor fit for the Unilin, Radke-Prausnitz, Freundlich and Redlich-Peterson models as it has been verified by the observation of the AR values as high as 12.17, 12.33, 12.50 and 13.00, respectively, and this verification reveals a very poor fit for the Redlich-Peterson model due to its AR value of 13.00 is higher than others.

3.1.4. Adsorption of AgNPs on Poly(ethylenimine) functionalized core-shell magnetic

The results (Table 9 in Supplementary materials) of ranking the values of arithmetic mean being obtained from every statistical analysis method for the kinetic models of AgNPs adsorption on PFC show that the statistical analysis for the fractal-like pseudo-first-order, fractal-like mixed 1, 2-order and fractal-like exponential models gives a very good fit to experimental data as their AR values of 2.00, 2.83 and 3.17, respectively, have been verified with a best fit being obtained for the fractal-like pseudo-first-order model because of its lowest AR value of 2.00. A good fit can be obtained for the fractal-like pseudo-second-order, Boyd, pseudo-second-order, power and mixed 1, 2-order models as their AR values of 4.17, 5.83, 6.67, 7.00 and 7.00, respectively, were verified. The model-data fit can be considered satisfactory for the Bangham, intraparticle diffusion and exponential models since the AR values were

verified as high as 7.67, 10.33 and 10.33, respectively. The statistical analysis for the pseudo-first-order, Avrami, first-order and second-order models gives a poor fit to the data due to their AR values of 11.67, 12.33, 14.50 and 14.50, respectively, were verified and this reveals a very poor fit being obtained for the first-order and second-order model because of the same their AR value of 14.50 is higher than others.

The analysis of using the values of arithmetic mean for the isotherm models of AgNPs adsorption on PFC (see Table 10 in Supplementary materials) shows that the only Freundlich model give a very good fit to experimental data as its AR value of 3.67 has been verified. A good fit can be found for the Radke-Prausnitz, Toth, Fritz-Schlunder, Khan, Brouers-Sotolongo, Koble-Corrigan and Baudu models as it can be verified by observation of their AR values of 4.33, 4.50, 5.33, 5.50, 6.67, 7.17 and 7.33, respectively. The verification of model-data fit carried out using the Langmuir-Freudlich, Maczewski-Jaroniec and Unilin models can be considered satisfactory since this view deals with the AR values as high as 8.00, 8.67 and 9.33, respectively. The statistical data analysis gives a poor fit for the Jovanovic, Langmuir, Hill and Redlich-Peterson models since it has been verified by the observation of the AR values as high as 11.83, 12.50, 12.50 and 12.67, respectively, and this verification reveals a very poor fit for the Redlich-Peterson model due to its AR value of 12.67 is higher than others.

3.1.5. Adsorption of AgNPs on *Aeromonas punctata*

The results (Table 11 in Supplementary materials) of ranking the values of arithmetic mean being obtained from every statistical analysis method for the kinetic models of AgNPs adsorption on AP show that the statistical analysis for the fractal-like mixed 1, 2-order, fractal-like pseudo-first-order and fractal-like exponential models gives a very good fit to experimental data because of their AR values of 1.5, 2.3 and 3.5, respectively, have been verified with a best fit being obtained for the fractal-like mixed 1, 2-order model to its lowest AR value of 1.5. A good fit can be obtained for the mixed 1, 2-order, fractal-like pseudo-second-order, pseudo-first-order and exponential models as their AR values of 5.7, 5.8, 5.7, 7.3 and 7.5, respectively, were verified. The model-data fit can be considered satisfactory for the Avrami, power, Bangham, pseudo-second-order and intraparticle diffusion models since the AR values were verified as high as 8.3, 8.7, 9.03 and 10.7, respectively. The statistical analysis for the Boyd, second-order and first-order models gives a poor fit to the data due to their AR values of 11.5, 13.5 and 13.7, respectively, were verified and this reveals a very poor fit being obtained for the first-order model because of its AR value of 13.7 is higher than others.

The analysis of using the values of arithmetic mean for the isotherm models of AgNPs adsorption on GB (see Table 12 in Supplementary materials) shows that the Maczewski-Jaroniec, Brouers-Sotolongo, Fritz-Schlunder and Baudu models give a very good fit to experimental data since their AR values of 1.33, 2.17, 3.00 and 3.50, respectively, have been verified with a best fit being obtained for the Maczewski-Jaroniec model as verified by its lowest AR value of 1.33. A good fit can be found for the Unilin, Langmuir-Freudlich and Koble-Corrigan models as it can be verified by observation of their AR values of 5.33, 6.50 and 6.50, respectively. The verification of model-data fit carried out using the Hill, Toth, Khan, Langmuir, Jovanovic and Radke-Prausnitz models can be considered satisfactory since this view deals with their AR values as high as 7.50, 9.50, 10.00, 11.00, 11.00 and 11.00, respectively. The statistical data analysis gives a poor fit for the Freundlich and Redlich-Peterson models as it has been verified by observation of the AR values as high as 13.50 and 15.00, respectively, and this verification reveals a very poor fit for the Redlich-Peterson model due to its AR value of 15.00 is higher than others.

3.2. Discussion

3.2.1. Application of the adsorption kinetic models

The error analysis has been one of the most applied tools for defining the best fitting adsorption models because it consists of different statistical methods for determining the values of such as R^2 , RMSE, E_{max} , E_{min} , MAPE and MAD (Ayawei et al., 2017; Madhavan et al., 2016; Sivarajasekar and Baskar, 2014). This analysis induces a ranking of the arithmetic mean in term of accuracy for every model. The results (Tables 3, 5, 7, 9, 11 in Supplementary materials) show the adsorption kinetic models for the adsorption of AgNPs do fit to the experimental data depending on type of the adsorbent. It is an inconsistency in the representational content of different models for the adsorption of AgNPs from aqueous solution and spectrum of the stimulating zone depends on AgNPs properties and environmental conditions (Sugand Liu, 2017). The experimental evidence of the existence of fractal-like mixed 1, 2-order model for modeling the adsorption of AgNPs on GB, AIOMP, FPC, PFC and AP gives a very good fit to the data as judged by all the AR values of below than 3.75 in spite of the analysis of using the values of E_{max} , E_{min} and MAPE as high as 4.00 for the adsorption of AgNPs on PFC from aqueous solution gives a good fit. A plot (Fig. 1) of q_t versus t for the fractal-like mixed 1, 2-order model shows that the trend curve is different depending on the adsorbent and can be expressed as parametric model with a growth curve followed exponential pattern within a specific range. The kinetics of AgNPs adsorption on GB, AIOMP, FPC, PFC or AP with an energetically heterogeneous surface determine the adsorption capacity and breakthrough time of the adsorbent of being characterized by its different surface chemical properties (Faya et al., 2017; Haerifar and Azizian, 2014). The statistical analysis of experimental data for the adsorption of AgNPs on GB, AIOMP, FPC and AP can be performed using the fractal-like pseudo-first-order, fractal-like exponential, fractal-like pseudo-second-order and mixed 1, 2-order models except for: (1) the use of mixed 1, 2-order model for modeling the adsorption of AgNPs on GB and PFC by using the R^2 , RMSE and MAPE values and AP by using the E_{min} and MAPE values and (2) the use of fractal-like pseudo-second-order model for modeling the adsorption of AgNPs on AP. This conclusion would be due to the use of these models to rank the values of arithmetic mean can provide a good fit within the data range as judged by their AR values of $3.75 \leq AR \leq 7.50$. Previous studies have found kinetics of AgNPs adsorption on GB, AIOMP, FPC and PFC followed a pseudo-second-order model (Polowczyk et al., 2015; Wu et al., 2017; Zhang et al., 2017; Zhou et al., 2017). It has been reported that the kinetics of adsorption of AgNPs on AP fitted best to pseudo-first-order (Khan et al., 2012). In this work, the use of pseudo-second-order, Boyd, power, exponential, pseudo-first-order, Bangham, Avrami and intraparticle diffusion models can be recommended for modeling the experimental data but it needs to be checked the reliability and validity on a case-by-case basis because of the error analysis of using the different statistical methods for determining the values of R^2 , RMSE, E_{max} , E_{min} , MAPE and MAD can have many reasons for coming to different conclusions of very good, good, satisfactory and poor fit to the experimental data. Experimental evidence (see Tables 3, 5, 7, 9, 11, 13 in Supplementary materials) shows that based on the application of arithmetic mean as a statistical measure the use of first-order and second-order models cannot be recommended for modeling the experimental data except the use of first order model for modeling the adsorption of AgNPs on FPC due to its statistical data analysis gives a poor fit to the data as judged by an AR value of higher than 11.25. In summary, comprehensive performance analysis of the fifteen kinetic models can rank that the use of the fractal-like mixed 1, 2-order describing the behaviors of adsorption of AgNPs is better than fractal-like pseudo-first-order,

better than fractal-like exponential, better than fractal-like pseudo-second-order, better than mixed 1, 2-order, better than pseudo-second-order, better than Boyd, better than Power, better than exponential, better than pseudo-first-order, better than Bangham, better than Avrami, better than intraparticle diffusion, better than first order, and better than second-order model as it can be verified by the overall average AR values of 1.61, 3.99, 4.66, 6.05, 7.00, 7.65, 7.94, 8.41, 8.51, 8.63, 8.98, 9.35, 10.70, 12.18, and 14.33, respectively (see Table 13 in Supplementary materials).

3.2.2. Application of the adsorption isotherm models

The error analysis may classify the ranking of the arithmetic mean in term of accuracy for the application of fifteen adsorption isotherm models. The results (Tables 4, 6, 8, 10, 12 in Supplementary materials) show that the isotherm models for modeling the adsorption of AgNPs do fit to the experimental data depending on the type of adsorbent. Even though the experimental evidence of using (1) the Fritz-Schlunder, Baudu and Khan models for modeling the adsorption of AgNPs on GB, (2) the Brouers-Sotolongo model for the adsorption of AgNPs on AIOMP, (3) the Koble-Corrigan and Toth models for the adsorption of AgNPs on FPC, (4) the Freundlich model for the adsorption of AgNPs on PFC and (5) the Maczewski-Jaroniec, Brouers-Sotolongo, Fritz-Schlunder and Baudu models for the adsorption of AgNPs on AP shows a very good fit to the experimental data as judged by the AR value of below 3.75, the statistical analysis of ranking the arithmetic mean verified that no one model can be considered as the most reliable estimate of adsorption isotherm parameters for the adsorption of AgNPs on all adsorbents of GB, AIOMP, FPC, PFC and AP. It has been reported that the experimental data best fitted the Langmuir model for the adsorption of AgNPs on GB, AIOMP, FPC and AP (Khan et al., 2012; Polowczyk et al., 2015; Wu et al., 2017; Zhou et al., 2017). Both Langmuir and Freundlich models fitted the experimental data well for the adsorption of AgNPs on PFC (Zhang et al., 2017). This study found that the most reliable way of analysing the experimental data for the adsorption of AgNPs on GB, AIOMP, FPC and AP can be suggested using the Fritz-Schlunder and Baudu models because of the use of these two models to rank the values of arithmetic mean can give a good fit to the data as judged by the AR values of $3.75 \leq AR \leq 7.50$. The trend curve is different depending on the adsorbent and this can be verified by plotting a curve of q_t versus t as shown in Fig. 2 for the application of Fritz-Schlunder model to describe the behaviours of AgNPs adsorption. This study of the adsorption of AgNPs on GB, AIOMP, FPC, PFC or AP evaluated by the fifteen isotherm models involves plotting the experimental data and finding the different behavior accumulation curves and this suggests that the physical and chemical properties of the adsorbent determine the adsorption capacity and concentration of AgNPs at equilibrium (Adane et al., 2015; Azeez et al., 2018). The application of Fritz-Schlunder, Brouers-Sotolongo, Baudu, Koble-Corrigan, Toth, Maczewski-Jaroniec, Khan, Langmuir-Freundlich, Hill, Radke-Prasnitz, Jovanovic and Unilin models can be recommended for modeling the experimental data since the AR values of less than 11.25 were verified in many cases; however, the verification of the reliability and validity of each model is important for any experimental data to provide guidance and clarity on the specific case of adsorption isotherm because of the error analysis of determining the values of R^2 , RMSE, E_{max} , E_{min} , MAPE and MAD can have each different conclusions of very good, good, satisfactory and poor fit to the experimental data. The experimental evidence of arithmetic mean verification (see Tables 4, 6, 8, 10, 12, 14 in Supplementary materials) shows that the use of Redlich-Peterson model cannot be recommended for modeling the adsorption of AgNPs on AIOMP, FPC, PFC and AP due to the statistical data analysis gives a poor fit to the experimental data as judged by the AR values of higher than

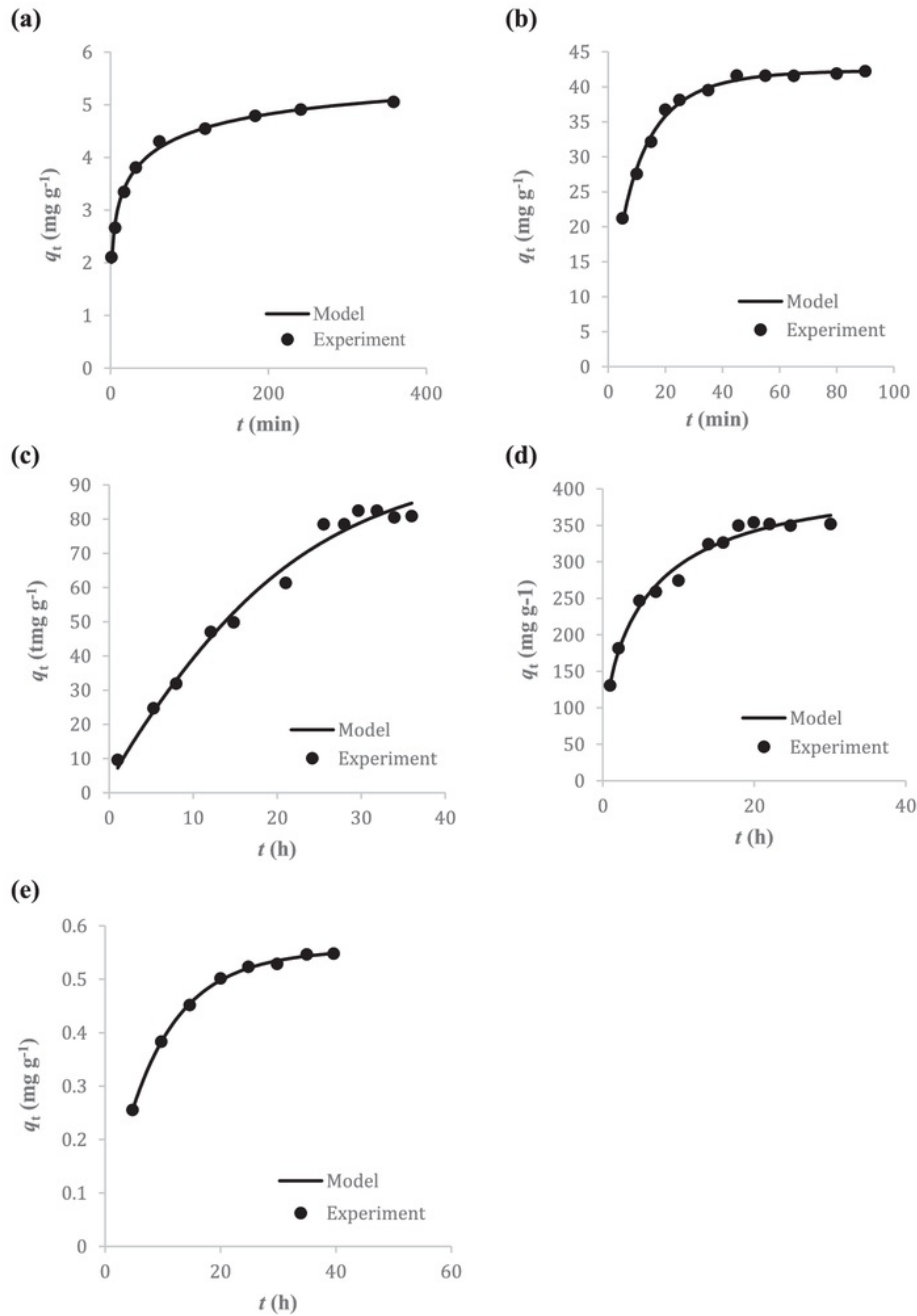


Fig. 1. Curve of plotting q_t versus t for assessing the behaviors of AgNPs adsorption on (a) GB, (b) AIOMP, (c) FPC, (d) PFC and (e) AP by the fractal-like mixed 1, 2-order kinetic model.

134 In general, the statistical analysis of the experimental data to evaluate the performance ranking of the fifteen isotherm models may conclude the Fritz-Schlunder better than Brouers-Sotolongo, better than Baudu, better than Koble-Corrigan, better than Toth, better than Maczewski-Jaroniec, better than Khan, better than Langmuir-Freudlich, better than Hill, better than Radke-Prausnitz,

better than Jovanovic, better than Unilin, better than Langmuir, better than Freundlich, and better than Redlich-Peterson as it can be verified by the overall average AR values of 4.17, 4.54, 4.87, 6.27, 6.30, 6.50, 6.60, 7.43, 8.43, 8.57, 9.73, 10.33, 11.37, 11.63, and 12.63, respectively (see Table 14 in Supplementary materials).

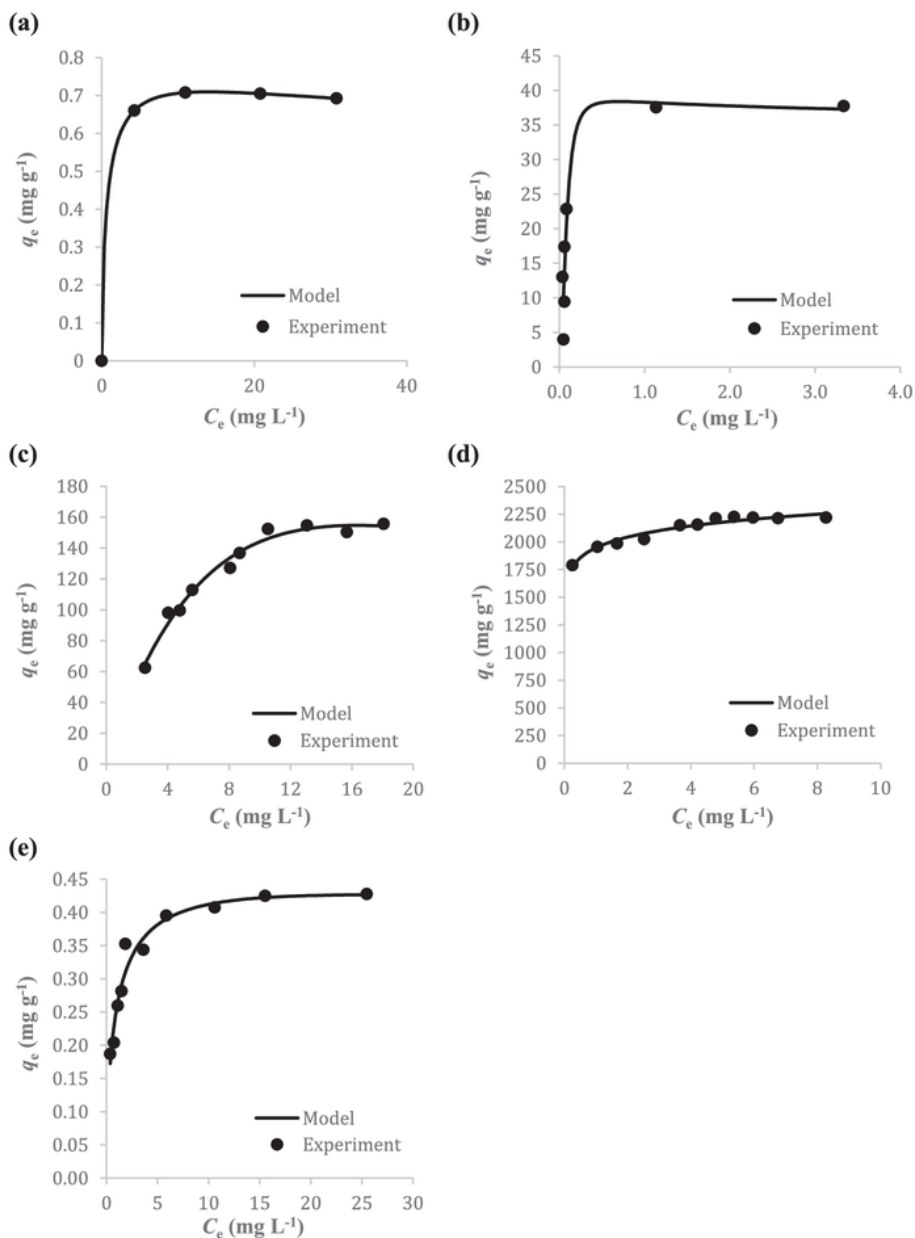


Fig. 2. Curve of plotting q_e versus C_e for assessing the behaviors of AgNPs adsorption on (a) GB, (b) AIOMP, (c) FPC, (d) PFC and (e) AP by the Fritz-Schlunder isotherm model.

4. Conclusions

This study used fifteen kinetic models and fifteen isotherm models together with six statistical analysis methods to assess the level of accuracy for the adsorption of AgNPs from aqueous solution onto the four types of adsorbent. The results of this study verified that the fractal-like mixed 1, 2-order model is the best one among the fifteen kinetic models to be used for describing the behaviors of adsorption of AgNPs on GB, AIOMP, FPC, PFC and AP and the Fritz-Schlunder and Baudu models are the most reliable isotherm models

to be used for describing the behaviors of adsorption of AgNPs on GB, AIOMP, PFC and AP. The verification of the reliability and validity of the match of these thirty models with experimental data would be important to provide guidance and clarity on the kinetic and isotherm studies of AgNPs adsorption on the GB, AIOMP, FPC, PFC and AP adsorbent. The application of other kinetic and isotherm models for studying the adsorption of AgNPs as well as the application of these thirty models for the adsorption of other nanoparticles onto different types of adsorbent would be interested in conducting researches in the future.

Conflict of interest

The authors declare that they have no conflict of interest.

Acknowledgements

The authors thank the financial supports from the Ministry of Higher Education of Malaysia for Research Grant No. R.J130000.7809.4F619, the Universiti Teknologi Malaysia for Research Grant No. QJ130000.2522.14H40 and the Ministry of Research, Technology and Higher Education of the Republic of Indonesia for Research Grant with the scheme of Penelitian Terapan Unggulan Perguruan Tinggi for the year 2018.

Appendix A. Supplementary data

Supplementary data related to this article can be found at <https://doi.org/10.1016/j.jenvman.2018.03.066>.

References

- Adane, B., Siraj, K., Meka, N., 2015. Kinetic, equilibrium and thermodynamic study of 2-chlorophenol adsorption onto *Ricinus communis* pericarp activated carbon from aqueous solutions. *Green Chem. Lett. Rev.* 8, 3–4, 1–12.
- Ayawei, N., Ebelegi, A.N., Wankasi, D., 2017. Modelling and interpretation of adsorption isotherms. *J. Chem.* 2017, 3039817.
- Azeez, L., Lateef, A., Adebisi, S.A., Oyedele, A.O., 2018. Novel biosynthesized silver nanoparticles from cowbess as adsorbent for Rhodamine B: equilibrium isotherm, kinetic and thermodynamic studies. *Appl. Water Sci.* 8, 322.
- Chen, C., 2003. Evaluation of equilibrium sorption isotherm equations. *Open Chem. Eng. J.* 7, 24–44.
- Chen, Z., Yang, P., Yuan, Z., Guo, J., 2017. Aerobic condition enhances bacteriostatic effects of silver nanoparticles in aquatic environment: an antimicrobial study on *Pseudomonas aeruginosa*. *Sci. Rep.* 7, 7398.
- Cheung, C.W., Porter, J.F., McKay, G., 2001. Sorption kinetic analysis for the removal of cadmium ions from effluents using bone char. *Water Res.* 35, 605–612.
- Conde-González, J.E., Peña-Méndez, E.M., Rybáková, S., Pasán, J., Ruiz-Pérez, C., Havel, J., 2016. Adsorption of silver nanoparticles from aqueous solution on copper-based metal organic frameworks (HKUST-1). *Chemosphere* 150, 659–666.
- Desireddy, A., Conn, B.E., Guo, J., Yoon, B., Barnett, R.N., Monahan, B.M., Kirschbaum, K., Griffith, W.P., Whetten, R.L., Landman, U., Bigioni, T.P., 2013. Ultrastable silver nanoparticles. *Nature* 501, 399–402.
- Fayaz, M., Zarifi, M.H., Abdolrazzagh, M., Shariaty, P., Hashisho, Z., Daneshmand, M., 2017. A novel technique for determining the adsorption capacity and breakthrough time of adsorbents using a noncontact high-resolution microwave resonator sensor. *Environ. Sci. Technol.* 51, 427–435.
- Fendlich, H., 1906. Over the adsorption in solution. *J. Phys. Chem.* 57, 1100–1107.
- Fritz, W., Schluender, E.U., 1974. Simultaneous adsorption equilibria of organic solutes in dilute aqueous solutions on activated carbon. *Chem. Eng. Sci.* 29, 1279–1282.
- Fulazzaky, M.A., 2011. Determining the resistance of mass transfer for adsorption of the surfactant onto granular activated carbons from hydrodynamic column. *Chem. Eng. J.* 166, 832–840.
- Fulazzaky, M.A., 2012. Analysis of global and sequential mass transfers for the adsorption of atrazine and simazine onto granular activated carbons from hydrodynamic column. *Anal. Methods* 4, 2396–2403.
- Fulazzaky, M.A., Khamidun, M.H., Omar, R., 2013. Understanding of mass transfer resistance for the adsorption of solute onto porous material from the modified mass transfer factor models. *Chem. Eng. J.* 228, 1023–1029.
- Fulazzaky, M.A., Khamidun, M.H., Din, M.F.M., Yusoff, A.R.M., 2014. Adsorption of phosphate from domestic wastewater treatment plant effluent onto the laterites in a hydrodynamic column. *Chem. Eng. J.* 258, 10–17.
- Fulazzaky, M.A., Majidnia, Z., Idris, A., 2017. Mass transfer kinetics of Cd(II) ions adsorption by titania polyvinylalcohol-alginate beads from aqueous solution. *Chem. Eng. J.* 308, 700–709.
- Gicheva, G., Yordanov, G., 2013. Removal of citrate-coated silver nanoparticles from aqueous dispersions by using activated carbon. *Coll. Surf. A Physicochem. Eng. Asp.* 431, 51–59.
- Gupta, V.K., Gupta, M., Sharma, S., 2001. Process development for the removal of lead and chromium from aqueous solutions using red mud - an aluminium industry waste. *Water Res.* 35, 1125–1134.
- Hafar, M., Azizian, S., 2013. An exponential kinetic model for adsorption at solid/solution interface. *Chem. Eng. J.* 215, 65–71.
- Hafar, M., Azizian, S., 2014. Fractal-like kinetics for adsorption on heterogeneous solid surfaces. *J. Phys. Chem.* 118, 1129–1134.
- Hameed, B.H., Tan, I.A.W., Ahmad, A.L., 2008. Adsorption isotherm, kinetic modeling and mechanism of 2,4,6-trichlorophenol on coconut husk-based activated carbon. *Chem. Eng. J.* 144, 235–244.
- Hill, A.V., 1910. The possible effects of the aggregation of the molecules of haemoglobin on its dissociation curves. *J. Physiol.* 40, 4–7.
- Ho, Y.S., McKay, G., 1998a. A comparison of chemisorption kinetic models applied to pollutant removal on various sorbents. *Process Saf. Environ. Prot.* 76, 332–340.
- Ho, Y.S., McKay, G., 1998b. Sorption of dye from aqueous solution by peat. *Chem. Eng. J.* 70, 115–124.
- Ismael, G.P., Clement, T.P., 2012. A modified Langmuir-Freundlich isotherm model for simulating pH-dependent adsorption effects. *J. Contam. Hydrol.* 129, 46–53.
- Khambhaty, Y., Mody, K., Basha, S., Jha, B., 2009. Kinetics, equilibrium and thermodynamic studies on biosorption of hexavalent chromium by dead fungal biomass of marine *Aspergillus Niger*. *Chem. Eng. J.* 145, 489–495.
- Khan, A.R., Al-Bahri, T.A., Al-Haddad, A., 1997. Adsorption of phenol based organic pollutants on activated carbon from multicomponent dilute aqueous solutions. *Water Res.* 31, 2102–2112.
- Khan, S.S., Mukherjee, A., Chandrasekaran, N., 2012. Adsorptive removal of silver nanoparticles (SNPs) from aqueous solution by *Aeromonas punctata* and its adsorption isotherm and kinetics. *Coll. Surf. B Biointerf.* 92, 156–160.
- Konig, R.A., Corrigan, T.E., 1952. Adsorption isotherms for pure hydrocarbons. *Ind. Eng. Chem.* 44, 383–387.
- Kumar, A., Vemula, P.K., Ajayan, P.M., John, G., 2008. Silver-nanoparticle-embedded antimicrobial paints based on vegetable oil. *Nat. Mater.* 7, 236–241.
- Kumar, P.S., Senthamarai, C., Durgadevi, A., 2014. Adsorption kinetics, mechanism, isotherm, and thermodynamic analysis of copper ions onto the surface modified agricultural waste. *Environ. Prog. Sustain. Energy* 33, 28–37.
- Lagergren, S., 1898. About the theory of so-called adsorption of soluble substances. *K. Sven. Vetenskapsakademiens Handl.* 24, 1–39.
- Langmuir, I., 1918. The adsorption of gases on plane surfaces of glass, mica and platinum. *J. Am. Chem. Soc.* 40, 1361–1403.
- Le Ouay, B., Stellacci, F., 2015. Antibacterial activity of silver nanoparticles: a surface science insight. *Nano Today* 10, 339–354.
- Lopes, E.C.N., dos Anjos, F.S.C., Vieira, E.F.S., Cestari, A.R., 2003. An alternative Avrami equation to evaluate kinetic parameters of the interaction of Hg(II) with thin chitosan membranes. *J. Coll. Interf. Sci.* 263, 542–547.
- Madhavan, D.B., Kitching, M., Mendham, D.S., Weston, C.J., Baker, T.G., 2016. Mid-infrared spectroscopy for rapid assessment of soil properties after land use change from pastures to *Eucalyptus globulus* plantations. *J. Environ. Manag.* 175, 57–75.
- Mazurek, A.W., 2010. Application of mixed order rate equations to adsorption of methylene blue on mesoporous carbons. *Appl. Surf. Sci.* 256, 5145–5152.
- Matias, M.S., Melegari, S.P., Vicentini, D.S., Matias, W.G., Ricordel, C., Hauchard, D., 2015. Synthetic wastewaters treatment by electrocoagulation to remove silver nanoparticles produced by different routes. *J. Environ. Manag.* 159, 147–157.
- McKay, G., Mesdaghinia, A., Nasser, S., Hadi, M., Aminabad, M.S., 2014. Optimum isotherms of dyes sorption by activated carbon: fractional theoretical capacity and error analysis. *Chem. Eng. J.* 251, 236–247.
- Naik, R.R., Stringer, S.J., Agarwal, G., Jones, S.E., Stone, M.O., 2002. Biomimetic synthesis and patterning of silver nanoparticles. *Nat. Mater.* 1, 169–172.
- Park, M., Im, J., Shin, M., Min, Y., Park, J., Cho, H., Park, S., Shim, M.-B., Jeon, S., Chung, D.-Y., Bae, J., Park, J., Jeong, U., Kim, K., 2012. Highly stretchable electric circuits from a composite material of silver nanoparticles and elastomeric fibers. *Nat. Nanotechnol.* 7, 803–809.
- Plazinski, W., Rudzinski, W., 2009. Kinetics of adsorption at solid/solution interfaces controlled by intraparticle diffusion: a theoretical analysis. *J. Phys. Chem.* 113, 12495–12501.
- Podder, M.S., Majumder, C.B., 2016. Sequestering of As(III) and As(V) from wastewater using a novel neem leaves/MnFe2O4 composite biosorbent. *Int. J. Phytoremed.* 18, 1237–1257.
- Polowczyk, I., Koźlecki, T., Bastrzyk, A., 2015. Adsorption of silver nanoparticles on glass beads surface. *Ads. Sci. Technol.* 33, 731–737.
- Prinos, M.E., Marr, L.C., 2010. Environmental and human health risks of aerosolized silver nanoparticles. *J. Air Waste Manag. Assoc.* 60, 770–781.
- Radke, C.J., Prausnitz, J.M., 1972. Adsorption of organic solutes from dilute aqueous solution of activated carbon. *Ind. Eng. Chem. Fundam.* 11, 445–451.
- Rania, F., Yousef, N.S., 2015. Equilibrium and kinetics studies of adsorption of copper (II) on natural biosorbent. *Int. J. Chem. Eng. Appl.* 6, 319–324.
- Rodríguez, A., García, J., Ovejero, G., Mestanza, M., 2009. Adsorption of anionic and cationic dyes on activated carbon from aqueous solutions: equilibrium and kinetics. *J. Hazard. Mater.* 172, 1311–1320.
- Royer, B., Cardoso, N.F., Lima, E.C., Vaghetti, J.C.P., Simon, N.M., Calvete, T., Veses, R.C., 2009. Applications of Brazilian pine-fruit shell in natural and carbonized forms as adsorbents to removal of methylene blue from aqueous solutions - kinetic and equilibrium study. *J. Hazard. Mater.* 164, 1213–1222.
- Ruiz-Baltazar, A., Reyes-López, S.Y., Tellez-Vasquez, O., Esparza, R., Rosas, G., Pérez, R., 2015. Analysis for the sorption kinetics of Ag nanoparticles on natural clinoptilolite. *Adv. Cond. Matter Phys.* 2015, 284518.
- Snahbeig, H., Bagheri, N., Ghorbanian, S.A., Hallajisani, A., Poorkarimi, S., 2013. A new adsorption isotherm model of aqueous solutions on granular activated carbon. *World J. Microbiol.* 9, 243–254.
- Sheng, Z., Liu, Y., 2017. Potential impacts of silver nanoparticles on bacteria in the aquatic environment. *J. Environ. Manag.* 191, 290–296.
- Silva, S.M., Sampaio, K.A., Ceriani, R., Verbe, R., Stevens, C., De Greyt, W., Meirelles, A.J.A., 2013. Adsorption of carotenes and phosphorus from palm oil onto acid activated bleaching earth: equilibrium, kinetics and thermodynamics. *J. Food Eng.* 118, 341–349.

46

Sivarajasekar, N., Baskar, R., 2014. Adsorption of basic red 9 onto activated carbon derived from immature cotton seeds: isotherm studies and error analysis. *Desalin. Water Treat.* 52, 7743–7765.

10

Tripathi, D.K., Tripathi, A., Shweta, Singh, S., Singh, Y., Vishwakarma, K., Yadav, G., Sharma, S., Singh, V.K., Mishra, R.K., Upadhyay, R.G., Dubey, N.K., Lee, Y., Chauhan, D.K., 2017. Uptake, accumulation and toxicity of silver nanoparticle in autotrophic plants, and heterotrophic microbes: a concentric review. *Front. Microbiol.* 8, 07.

89

Valenzuela, D.P., Myers, A.L., 1989. *Adsorption Equilibria Data Handbook*. Prentice-Hall, New Jersey.

35

Viegas, R.M., Campinas, M., Costa, H., Rosa, M.J., 2014. How do the HSDM and Boyd's model compare for estimating intraparticle diffusion coefficients in adsorption processes. *Adsorption* 20, 737–746.

51

Wang, S., Boyjoo, Y., Choueib, A., Zhu, Z.H., 2005. Removal of dyes from aqueous solution using fly ash and red mud. *Water Res.* 39, 129–138.

1

Wu, M., Li, Y., Yue, R., Zhang, X., Huang, Y., 2017. Removal of silver nanoparticles by mussel-inspired Fe₃O₄@ polydopamine core-shell microspheres and its use as efficient catalyst for methylene blue reduction. *Sci. Rep.* 7, 42773.

Zarei, A.R., Barghak, F., 2015. Fast and efficient adsorption of Ag nanoparticles by sodium montmorillonite nanoclay from aqueous systems. *J. Chem. Res.* 39, 542–545.

31

Zhang, X.-F., Liu, Z.-C., Shen, W., Gurunathan, S., 2016. Silver nanoparticles: synthesis, characterization, properties, applications, and therapeutic approaches. *Int. J. Mol. Sci.* 17, 1534.

16

Zhang, X., Zhang, Y., Zhang, X., Li, S., Huang, Y., 2017. Nitrogen rich core-shell magnetic mesoporous silica as an effective adsorbent for removal of silver nanoparticles from water. *J. Hazard. Mater.* 337, 1–9.

1

Zhou, X.-x., Li, Y.-j., Liu, J.-f., 2017. Highly efficient removal of silver-containing nanoparticles in waters by aged iron oxide magnetic particles. *ACS Sustain. Chem. Eng.* 5, 5468–5476.

Application of the kinetic and isotherm models for better understanding of the behaviors of silver nanoparticles adsorption onto different adsorbents

ORIGINALITY REPORT

39%

SIMILARITY INDEX

31%

INTERNET SOURCES

36%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

1

coeeits.com

Internet Source

5%

2

dns2.asia.edu.tw

Internet Source

3%

3

Sivarajasekar, N., and R. Baskar. "Adsorption of basic red 9 onto activated carbon derived from immature cotton seeds: isotherm studies and error analysis", *Desalination and Water Treatment*, 2014.

Publication

1%

4

Saeid Zarei, Mahmood Niad, Hossein Raanaei. "The removal of mercury ion pollution by using Fe₃O₄-nanocellulose: Synthesis, characterizations and DFT studies", *Journal of Hazardous Materials*, 2018

Publication

1%

5

eprints.uthm.edu.my

Internet Source

1%

6

M.S. Podder, C.B. Majumder. "Application of granular activated carbon/MnFe₂O₄ composite immobilized on *C. glutamicum* MTCC 2745 to remove As(III) and As(V): Kinetic, mechanistic and thermodynamic studies", *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, 2016

Publication

1%

7

ncsu.edu
Internet Source

1%

8

Mane, V.S.. "Kinetic and equilibrium isotherm studies for the adsorptive removal of Brilliant Green dye from aqueous solution by rice husk ash", *Journal of Environmental Management*, 200709

Publication

1%

9

M. S. Podder, C. B. Majumder. "Biosorption of As(III) and As(V) on the surface of TW/MnFe₂O₄ composite from wastewater: kinetics, mechanistic and thermodynamics", *Applied Water Science*, 2016

Publication

<1%

10

Parteek Prasher, Manjeet Singh, Harish Mudila. "Oligodynamic Effect of Silver Nanoparticles: a Review", *BioNanoScience*, 2018

Publication

<1%

11

repositorio.ufop.br

Internet Source

<1%

12

asia.edu.tw

Internet Source

<1%

13

Muzammil Anjum, Rajeev Kumar, S.M. Abdelbasir, M.A. Barakat. "Carbon nitride/titania nanotubes composite for photocatalytic degradation of organics in water and sludge: Pre-treatment of sludge, anaerobic digestion and biogas production", Journal of Environmental Management, 2018

Publication

<1%

14

nanoscalereslett.springeropen.com

Internet Source

<1%

15

Andressa M. Kubo, Luiz F. Gorup, Luciana S. Amaral, Edson R. Filho, Emerson R. Camargo. "Kinetic Control of Microtubule Morphology Obtained by Assembling Gold Nanoparticles on Living Fungal Biotemplates", Bioconjugate Chemistry, 2016

Publication

<1%

16

www.mdpi.com

Internet Source

<1%

17

Tono Saksono, Mohamad Ali Fulazzaky, Zamah Sari. "Geodetic analysis of disputed accurate qibla direction", Journal of Applied

<1%

Geodesy, 2018

Publication

18

Thi Nhung Tran, Do-Gun Kim, Seok-Oh Ko.
"Adsorption Mechanisms of Manganese (II) Ions
onto Acid-treated Activated Carbon", KSCE
Journal of Civil Engineering, 2018

Publication

<1%

19

www.lume.ufrgs.br

Internet Source

<1%

20

Bouزيد, S., A. Khenifi, K. A. Bennabou, R.
Trujillano, M. A. Vicente, and Z. Derriche.
"Removal of Orange II by Phosphonium-
Modified Algerian Bentonites", Chemical
Engineering Communications, 2014.

Publication

<1%

21

citeseerx.ist.psu.edu

Internet Source

<1%

22

Reza Tabaraki, Mina Khodabakhshi. " Multidye
Biosorption: Wavelet Neural Network Modeling
and Taguchi L Orthogonal Array Design ",
CLEAN - Soil, Air, Water, 2017

Publication

<1%

23

Halim, Mohd Hakim Ab Anuar, Aznah Nor Ja.
"Influence of high temperature on the
performance of aerobic granular sludge in
biological treatment ", Journal of
Environmental Management, Dec 15 2016

<1%

Issue

Publication

24

repositorio.ufla.br

Internet Source

<1%

25

www.solid-earth.net

Internet Source

<1%

26

link.springer.com

Internet Source

<1%

27

tez.sdu.edu.tr

Internet Source

<1%

28

www.jesc.ac.cn

Internet Source

<1%

29

Liu Bo, Zhang Shengen, Chein-Chi Chang. "Emerging Pollutants – Part II: Treatment", *Water Environment Research*, 2017

Publication

<1%

30

Xiaoye Zhang, Yao Zhang, Xiaodan Zhang, Siqi Li, Yuming Huang. "Nitrogen rich core–shell magnetic mesoporous silica as an effective adsorbent for removal of silver nanoparticles from water", *Journal of Hazardous Materials*, 2017

Publication

<1%

31

www.frontiersin.org

Internet Source

<1%

32

www.environmentaljournal.org

Internet Source

<1%

33

Mohammad H. Zarifi, Abedeh Gholidoust,
Mohammad Abdolrazzaghi, Pooya Shariaty,
Zaher Hashisho, Mojgan Daneshmand.

"Sensitivity enhancement in planar microwave
active-resonator using metal organic
framework for CO₂ detection", Sensors and
Actuators B: Chemical, 2017

Publication

<1%

34

jwrd.iwaponline.com

Internet Source

<1%

35

www.degois.pt

Internet Source

<1%

36

jestec.taylors.edu.my

Internet Source

<1%

37

nardus.mpn.gov.rs

Internet Source

<1%

38

file.scirp.org

Internet Source

<1%

39

Shakiba Naeimi, Hossein Faghihian.

"Remediation of pharmaceutical contaminated
water by use of magnetic functionalized metal
organic framework. Physicochemical study of
doxycycline adsorption", Water and

<1%

-
- | | | |
|----|---|-----|
| 40 | jyx.jyu.fi
Internet Source | <1% |
|----|---|-----|
-
- | | | |
|----|---|-----|
| 41 | Álvarez-Torrellas, S., G. Ovejero, R. García-Lovera, A. Rodríguez, and J. García. "Synthesis of a mesoporous carbon from peach stones for adsorption of basic dyes from wastewater: kinetics, modeling, and thermodynamic studies", <i>Clean Technologies and Environmental Policy</i> , 2016.
Publication | <1% |
|----|---|-----|
-
- | | | |
|----|--|-----|
| 42 | Lin Yuan, Curtis J. Richardson, Mengchi Ho, C. Wesley Willis, Benjamin P. Colman, Mark R. Wiesner. "Stress Responses of Aquatic Plants to Silver Nanoparticles", <i>Environmental Science & Technology</i> , 2018
Publication | <1% |
|----|--|-----|
-
- | | | |
|----|---|-----|
| 43 | www.matec-conferences.org
Internet Source | <1% |
|----|---|-----|
-
- | | | |
|----|---|-----|
| 44 | mdpi.com
Internet Source | <1% |
|----|---|-----|
-
- | | | |
|----|---|-----|
| 45 | www.sajs.co.za
Internet Source | <1% |
|----|---|-----|
-
- | | | |
|----|--|-----|
| 46 | "Recent Advances in Chemical Engineering", Springer Nature, 2016 | <1% |
|----|--|-----|

47 onlinelibrary.wiley.com <1 %
Internet Source

48 ijens.org <1 %
Internet Source

49 Mandal, Abhishek, and Neera Singh. "Kinetic and isotherm error optimization studies for adsorption of atrazine and imidacloprid on bark of Eucalyptus tereticornis L.", Journal of Environmental Science and Health Part B, 2016. <1 %
Publication

50 Guilherme Dilarri, Carlos Renato Corso. " immobilized onto cross-linked chitosan beads: application of a novel material for the removal of dye toxicity ", Environmental Technology, 2017 <1 %
Publication

51 iahr.tandfonline.com.tandf-prod.literatumonline.com <1 %
Internet Source

52 www.docme.ru <1 %
Internet Source

53 iwaponline.com <1 %
Internet Source

Qing-xiu JING, Yun-yan WANG, Li-yuan CHAI,

- 54 Chong-jian TANG, Xiao-dong HUANG, Huan GUO, Wei WANG, Wei YOU. "Adsorption of copper ions on porous ceramsite prepared by diatomite and tungsten residue", Transactions of Nonferrous Metals Society of China, 2018
Publication <1%
-
- 55 journal.frontiersin.org
Internet Source <1%
-
- 56 Lu, Ning. "Generalized Soil Water Retention Equation for Adsorption and Capillarity", Journal of Geotechnical and Geoenvironmental Engineering, 2016.
Publication <1%
-
- 57 repository.ubn.ru.nl
Internet Source <1%
-
- 58 "Green Adsorbents for Pollutant Removal", Springer Nature, 2018
Publication <1%
-
- 59 Kumar, Arvind, and Hara Mohan Jena. "Removal of methylene blue and phenol onto prepared activated carbon from Fox nutshell by chemical activation in batch and fixed-bed column", Journal of Cleaner Production, 2016.
Publication <1%
-
- 60 www.springerprofessional.de
Internet Source <1%
-

61

repositorio-aberto.up.pt

Internet Source

<1%

62

mx.nthu.edu.tw

Internet Source

<1%

63

www.m-hikari.com

Internet Source

<1%

64

Liu, C., Y. Yang, and N. Wan. "Kinetic studies of phosphate adsorption onto construction solid waste (CSW)", *Water Quality Research Journal of Canada*, 2014.

Publication

<1%

65

Shamik Chowdhury, Papita Das. "Linear and Nonlinear Regression Analyses for Binary Sorption Kinetics of Methylene Blue and Safranin onto Pretreated Rice Husk", *Bioremediation Journal*, 2011

Publication

<1%

66

Ahmadi, Mohammad Ali, and Seyed Shadizadeh. "Experimental and Theoretical Study of a New Plant Derived Surfactant Adsorption on Quartz Surface: Kinetic and Isotherm Methods", *Journal of Dispersion Science and Technology*, 2015.

Publication

<1%

67

repository.tudelft.nl

Internet Source

<1%

68

tdx.cat

Internet Source

<1%

69

Monireh Haerifar, Saeid Azizian. "An exponential kinetic model for adsorption at solid/solution interface", Chemical Engineering Journal, 2013

Publication

<1%

70

www.thieme-connect.de

Internet Source

<1%

71

Saeid Zarei, Mahmood Niad. "Cystoseira myricaas for mercury (II) uptake: Isotherm, kinetics, thermodynamic, response surface methodology and fuzzy modeling", Journal of the Taiwan Institute of Chemical Engineers, 2017

Publication

<1%

72

M.S. Podder, C.B. Majumder. "Bacteria immobilization on neem leaves/MnFe₂O₄ composite surface for removal of As(III) and As(V) from wastewater", Arabian Journal of Chemistry, 2015

Publication

<1%

73

www.icontrolpollution.com

Internet Source

<1%

74

Luqmon Azeez, Agbaje Lateef, Segun A. Adebisi, Abdulrasaq O. Oyedeji. "Novel

<1%

biosynthesized silver nanoparticles from cobweb as adsorbent for Rhodamine B: equilibrium isotherm, kinetic and thermodynamic studies", Applied Water Science, 2018

Publication

75

Lv, L.. "Uptake of chloride ion from aqueous solution by calcined layered double hydroxides: Equilibrium and kinetic studies", Water Research, 200602

Publication

<1%

76

Despina vamvuka, Stelios Dermitzakis, Despina Pentari, Stelios Sfakiotakis. "Valorization of Meat and Bone Meal through Pyrolysis for Soil Amendment or Lead Adsorption from Wastewaters", Food and Bioproducts Processing, 2018

Publication

<1%

77

Izabela Polowczyk, Tomasz Koźlecki, Anna Bastrzyk. "Adsorption of Silver Nanoparticles on Glass Beads Surface", Adsorption Science & Technology, 2015

Publication

<1%

78

Setareh Eris, Saeid Azizian. "Analysis of adsorption kinetics at solid/solution interface using a hyperbolic tangent model", Journal of Molecular Liquids, 2017

Publication

<1%

79

www.gjesm.net

Internet Source

<1%

80

Merat Ghanei, Abosaeed Rashidi, Habib-Allah Tayebi, Mohammad Esmail Yazdanshenas. "Removal of Acid Blue 25 from Aqueous Media by Magnetic-SBA-15/CPAA Super Adsorbent: Adsorption Isotherm, Kinetic, and Thermodynamic Studies", Journal of Chemical & Engineering Data, 2018

Publication

<1%

81

Oubagaranadin, J.U.K.. "Evaluation of Fuller's earth for the adsorption of mercury from aqueous solutions: A comparative study with activated carbon", Journal of Hazardous Materials, 20070402

Publication

<1%

82

issuu.com

Internet Source

<1%

83

Mohamad Ali Fulazzaky, Maria Nuid, Azmi Aris, Khalida Muda. "Kinetics and mass transfer studies on the biosorption of organic matter from palm oil mill effluent by aerobic granules before and after the addition of *Serratia marcescens* SA30 in a sequencing batch reactor", Process Safety and Environmental Protection, 2017

Publication

<1%

84

Mohamad Ali Fulazzaky, Mohd Hairul Khamidun, Mohd Fadhil Md Din, Abdull Rahim Mohd Yusoff. "Adsorption of phosphate from domestic wastewater treatment plant effluent onto the laterites in a hydrodynamic column", *Chemical Engineering Journal*, 2014

Publication

<1%

85

S. Sobhanardakani, R. Zandipak. " Cerium dioxide nanoparticles decorated on CuFe O nanofibers as an effective adsorbent for removal of estrogenic contaminants (bisphenol A and 17- α ethinylestradiol) from water ", *Separation Science and Technology*, 2018

Publication

<1%

86

Kakavandi, Babak, Ali Esrafil, Anoushiravan Mohseni-Bandpi, Ahmad Jonidi Jafari, and Roshanak Rezaei Kalantary. "Magnetic Fe₃O₄@C nanoparticles as adsorbents for removal of amoxicillin from aqueous solution", *Water Science & Technology*, 2014.

Publication

<1%

87

Taiana M. Deboni, Eduardo A. C. Batista, Antonio J. A. Meirelles. "Equilibrium, Kinetics, and Thermodynamics of Soybean Oil Deacidification Using a Strong Anion Exchange Resin", *Industrial & Engineering Chemistry Research*, 2015

Publication

<1%

88

media.neliti.com

Internet Source

<1%

89

J. Helminen. "Ammonium Removal from Aqueous Solutions Using Sulfonated Polystyrene Grafted Silica Gel Sorbent", *Separation Science and Technology*, 5/1/2006

Publication

<1%

90

Xiong Zheng, Juan Wang, Yinguang Chen, Yuanyuan Wei. "Comprehensive analysis of transcriptional and proteomic profiling reveals silver nanoparticles-induced toxicity to bacterial denitrification", *Journal of Hazardous Materials*, 2018

Publication

<1%

91

T. V. N. Padmesh, K. Vijayaraghavan, G. Sekaran, M. Velan. " Application of Two-and Three-Parameter Isotherm Models: Biosorption of Acid Red 88 onto ", *Bioremediation Journal*, 2007

Publication

<1%

92

Saeed Nazari Kudahi, Ali Reza Noorpoor, Niyaz Mohammad Mahmoodi. "Determination and analysis of CO₂ capture kinetics and mechanisms on the novel graphene-based adsorbents", *Journal of CO₂ Utilization*, 2017

Publication

<1%

93

Hossain, M.A., H.H. Ngo, W.S. Guo, T.V. Nguyen, and S. Vigneswaran. "Performance of cabbage and cauliflower wastes for heavy metals removal", *Desalination and Water Treatment*, 2014.

Publication

<1%

94

Sasireka Senniappan, Shanmughaprabha Palanisamy, Sabarathinam Shanmugam, Selvakumari Gobalsamy. " Adsorption of Pb (II) from aqueous solution by seed carbon: Kinetics, equilibrium, and desorption studies ", *Environmental Progress & Sustainable Energy*, 2017

Publication

<1%

95

scholar.sun.ac.za

Internet Source

<1%

96

Paola Rodríguez-Estupiñán, Alessandro Erto, Liliana Giraldo, Juan Moreno-Piraján. "Adsorption of Cd (II) on Modified Granular Activated Carbons: Isotherm and Column Study", *Molecules*, 2017

Publication

<1%

97

www.eemj.icpm.tuiasi.ro

Internet Source

<1%

98

Bhatnagar, A.. "Utilization of agro-industrial and municipal waste materials as potential

<1%

adsorbents for water treatment-A review",
Chemical Engineering Journal, 20100301

Publication

99

Joginder Singh, Renu Sharma, Amjad Ali. "Application of charcoal for desalinating Ni(II) and Zn(II) from aqueous solutions through batch mode ", Journal of Water Reuse and Desalination, 2013

Publication

100

ethesis.nitrkl.ac.in

Internet Source

101

Yurtsever, M.. "Biosorption of Pb(II) ions by modified quebracho tannin resin", Journal of Hazardous Materials, 20090415

Publication

102

Chukwunonso P. Okoli, Augustine E. Ofomaja. "Degree of time dependency of kinetic coefficient as a function of adsorbate concentration; new insights from adsorption of tetracycline onto monodispersed starch-stabilized magnetic nanocomposite", Journal of Environmental Management, 2018

Publication

103

Liu, Jianfei, Jiajun Chen, Lin Jiang, and Xingwei Wang. "Adsorption of fluoranthene in surfactant solution on activated carbon: equilibrium, thermodynamic, kinetic studies",

<1%

<1%

<1%

<1%

<1%

- 104 Wang, S.. "Novel applications of red mud as coagulant, adsorbent and catalyst for environmentally benign processes", Chemosphere, 200808 <1%

Publication

- 105 Fulazzaky, Mohamad Ali, Zohreh Majidnia, and Ani Idris. "Mass transfer kinetics of Cd(II) ions adsorption by titania polyvinylalcohol-alginate beads from aqueous solution", Chemical Engineering Journal, 2017. <1%

Publication

- 106 Neetu Singh, Chandrajit Balomajumder. "Equilibrium isotherm and kinetic studies for the simultaneous removal of phenol and cyanide by use of *S. odorifera* (MTCC 5700) immobilized on coconut shell activated carbon", Applied Water Science, 2016 <1%

Publication

- 107 Selatnia, A.. "Biosorption of Cd²⁺ from aqueous solution by a NaOH-treated bacterial dead *Streptomyces rimosus* biomass", Hydrometallurgy, 200411 <1%

Publication

- 108 www.cheric.org

<1%

109 repository.ust.hk
Internet Source

<1%

110 Zohreh Majidnia, Mohamad Ali Fulazzaky.
"Photoreduction of Pb(II) ions from aqueous
solution by titania polyvinylalcohol–alginate
beads", Journal of the Taiwan Institute of
Chemical Engineers, 2016
Publication

<1%

111 Rashidi, Sepideh, Manouchehr Nikazar, Ali
Vaziri Yazdi, and Reza Fazaeli. "Optimized
photocatalytic degradation of Reactive Blue 2
by TiO₂/UV process", Journal of Environmental
Science and Health Part A, 2014.
Publication

<1%

112 Basha, Shaik, Z. V. P. Murthy, and B. Jha.
"Sorption of Hg(II) from Aqueous Solutions
onto *Carica papaya*: Application of Isotherms",
Industrial & Engineering Chemistry Research,
2008.
Publication

<1%

113 Monireh Haerifar, Saeid Azizian. "Fractal-Like
Kinetics for Adsorption on Heterogeneous Solid
Surfaces", The Journal of Physical Chemistry
C, 2014
Publication

<1%

114	<p>Wan, Y., D. Sun, and J. Labadie. "MODELLING EVALUATION OF DAM REMOVAL IN THE CONTEXT OF RIVER ECOSYSTEM RESTORATION : MODELLING EVALUATION OF DAM REMOVAL", River Research and Applications, 2014.</p> <p>Publication</p>	<1%
115	<p>bobgaydos.blogspot.com</p> <p>Internet Source</p>	<1%
116	<p>www.nuigalway.ie</p> <p>Internet Source</p>	<1%
117	<p>Senthil Kumar, P., C. Senthamarai, and A. Durgadevi. "Adsorption Kinetics, Mechanism, Isotherm, and Thermodynamic Analysis of Copper Ions onto the Surface Modified Agricultural Waste", Environmental Progress & Sustainable Energy, 2012.</p> <p>Publication</p>	<1%
118	<p>eprints.utar.edu.my</p> <p>Internet Source</p>	<1%
119	<p>sabiod.univ-tln.fr</p> <p>Internet Source</p>	<1%
120	<p>Mohamad Ali Fulazzaky, Mohd Hairul Khamidun, Roslan Omar. "Understanding of mass transfer resistance for the adsorption of solute onto porous material from the modified</p>	<1%

mass transfer factor models", Chemical Engineering Journal, 2013

Publication

121

journal-cdn.frontiersin.org

Internet Source

<1%

122

Uma Pongkitdachoti, Fuangfa Unob. "Simultaneous adsorption of silver nanoparticles and silver ions on large pore mesoporous silica", Journal of Environmental Chemical Engineering, 2018

Publication

<1%

123

Yong Tian, Ping Liu, Xiufang Wang, Hansen Lin. "Adsorption of malachite green from aqueous solutions onto ordered mesoporous carbons", Chemical Engineering Journal, 2011

Publication

<1%

124

horizon.documentation.ird.fr

Internet Source

<1%

125

Mandu I. Inyang, Bin Gao, Ying Yao, Yingwen Xue, Andrew Zimmerman, Ahmed Mosa, Pratap Pullammanappallil, Yong Sik Ok, Xinde Cao. "A review of biochar as a low-cost adsorbent for aqueous heavy metal removal", Critical Reviews in Environmental Science and Technology, 2015

Publication

<1%

Krishnan, K.A.. "Kinetic and equilibrium

- 126 modelling of cobalt(II) adsorption onto bagasse pith based sulphurised activated carbon", Chemical Engineering Journal, 20080401
Publication <1%
-
- 127 N. S. Kumar, M. Suguna, M. V. Subbaiah, A. S. Reddy, N. P. Kumar, A. Krishnaiah. "Adsorption of Phenolic Compounds from Aqueous Solutions onto Chitosan-Coated Perlite Beads as Biosorbent", Industrial & Engineering Chemistry Research, 2010
Publication <1%
-
- 128 Wu, Yan, Hanjin Luo, and Hou Wang. "Efficient Removal of Congo Red from Aqueous Solutions by Surfactant-Modified Hydroxo Aluminum/Graphene Composites", Separation Science and Technology, 2014.
Publication <1%
-
- 129 Raji, Foad, Majid Pakizeh, Alireza Saraeian, and Mojtaba Raji. "A detailed study on adsorption isotherms of Hg(II) removal from aqueous solutions using nanostructured sorbent ZnCl₂-MCM-41", Desalination and Water Treatment, 2015.
Publication <1%
-
- 130 Clément Levard, E. Matt Hotze, Gregory V. Lowry, Gordon E. Brown. "Environmental Transformations of Silver Nanoparticles: <1%

Impact on Stability and Toxicity",
Environmental Science & Technology, 2012

Publication

131 Ma, Z.. "Adsorption removal of ammonium and phosphate from water by fertilizer controlled release agent prepared from wheat straw", Chemical Engineering Journal, 20110715

Publication

132 www.cafsti.org

Internet Source

133 Faghihian, Hossein, Seyed Nezamoddin Mirsattari, and Khadijeh Asghari. "Kinetics & thermodynamics of Cu(II) adsorption by imprinted salen-functionalized silica gel", Desalination and Water Treatment, 2014.

Publication

134 www.scribd.com

Internet Source

135 tci-thaijo.org

Internet Source

136 Seyed Mohammadreza Miraboutalebi, Soheil Kordmirza Nikouzad, Mohammad Peydayesh, Nima Allahgholi, Leila Vafajoo, Gordon McKay. "Methylene blue adsorption via maize silk powder: Kinetic, equilibrium, thermodynamic studies and residual error analysis", Process

Safety and Environmental Protection, 2017

Publication

137	iel.vscht.cz Internet Source	<1%
138	www.ceaa.gc.ca Internet Source	<1%
139	era.library.ualberta.ca Internet Source	<1%
140	www.ncsu.edu Internet Source	<1%
141	dspace.lib.ntua.gr Internet Source	<1%
142	www.doria.fi Internet Source	<1%
143	www.scielo.br Internet Source	<1%
144	Gunay, A.. "Lead removal from aqueous solution by natural and pretreated clinoptilolite: Adsorption equilibrium and kinetics", Journal of Hazardous Materials, 20070719 Publication	<1%
145	ecommons.usask.ca Internet Source	<1%
146	studentsrepo.um.edu.my Internet Source	<1%

147 Mohamad Ali Fulazzaky, Zohreh Majidnia, Ani Idris. "Mass transfer kinetics of Cd(II) ions adsorption by titania polyvinylalcohol-alginate beads from aqueous solution", Chemical Engineering Journal, 2017
Publication <1%

148 etheses.bham.ac.uk
Internet Source <1%

149 www.nature.com
Internet Source <1%

150 jehse.biomedcentral.com
Internet Source <1%

151 Khorshidi, Niyayesh, and AmirReza Azadmehr. "Characterization and Adsorption Properties of Oxalate-Loaded Hematite Composite for Cd (II) and Pb (II) Adsorption: Equilibrium Models, Thermodynamic, and Kinetic Studies", Separation Science and Technology, 2016.
Publication <1%

152 Hyun Min Jang, Seunghyun Yoo, Yong-Keun Choi, Sunkyu Park, Eunsung Kan. "Adsorption isotherm, kinetic modeling and mechanism of tetracycline on Pinus taeda -derived activated biochar", Bioresource Technology, 2018
Publication <1%

Fabio Montagnaro, Marco Balsamo. "Deeper

153 insights into fractal concepts applied to liquid-phase adsorption dynamics", Fuel Processing Technology, 2014 <1%

Publication

154 Foo, K.Y.. "Insights into the modeling of adsorption isotherm systems", Chemical Engineering Journal, 20100101 <1%

Publication

155 Pankaj Gogoi, Pooja Adhikari, Tarun K. Maji. "Bioremediation of arsenic from water with citric acid cross-linked water hyacinth (E. crassipes) root powder", Environmental Monitoring and Assessment, 2017 <1%

Publication

156 Chuncai Yao, Tianjiao Chen. "A weighted average kinetic equation and its application in estimating mass transfer coefficients in liquid phase adsorption", Biophysical Chemistry, 2018 <1%

Publication

157 Dominik Janacek, Libor Kvitek, Martina Karlikova, Kristyna Pospiskova, Ivo Safarik. "Removal of silver nanoparticles with native and magnetically modified halloysite", Applied Clay Science, 2018 <1%

Publication

158 Mahwish Asgher. "Biosorption of Reactive Dyes: A Review", Water Air & Soil Pollution, <1%

12/16/2011

Publication

159 Kerstin I. Andersson, Marie Eriksson, Magnus Norgren. "Removal of Lignin from Wastewater Generated by Mechanical Pulping Using Activated Charcoal and Fly Ash: Adsorption Kinetics", Industrial & Engineering Chemistry Research, 2011 <1%

Publication

160 El-Sikaily, A.. "Removal of toxic chromium from wastewater using green alga *Ulva lactuca* and its activated carbon", Journal of Hazardous Materials, 20070905 <1%

Publication

161 Katarzyna Ignatowicz. "Chapter 35 Low-Cost Sorbent for Removing Pesticides during Water Treatment", InTech, 2011 <1%

Publication

162 Coleman, N.J.. "Sorptions of Co^{2+} and Sr^{2+} by waste-derived 11 A tobermorite", Waste Management, 2006 <1%

Publication

163 Kim E. Sapsford, W. Russ Algar, Lorenzo Berti, Kelly Boeneman Gemmill et al. "Functionalizing Nanoparticles with Biological Molecules: Developing Chemistries that Facilitate Nanotechnology", Chemical Reviews, 2013 <1%

164

Achmad Syafiuddin, Salmiati, Mohd Razman Salim, Ahmad Beng Hong Kueh, Tony Hadibarata, Hadi Nur. "A Review of Silver Nanoparticles: Research Trends, Global Consumption, Synthesis, Properties, and Future Challenges", Journal of the Chinese Chemical Society, 2017

<1%

Publication

Exclude quotes Off

Exclude matches Off

Exclude bibliography Off

Application of the kinetic and isotherm models for better understanding of the behaviors of silver nanoparticles adsorption onto different adsorbents

GRADEMARK REPORT

FINAL GRADE

/10

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7

PAGE 8

PAGE 9

PAGE 10

PAGE 11

PAGE 12
